

Antti Aronen





SCHOTT

What advantages does our floated borosilicate glass offer for windshield glazing?


Presented by
Dr. Juliane Brandt-Slowik

The Structure of a Material Determines its Properties, and the Properties Enable the use of the Material in certain Applications

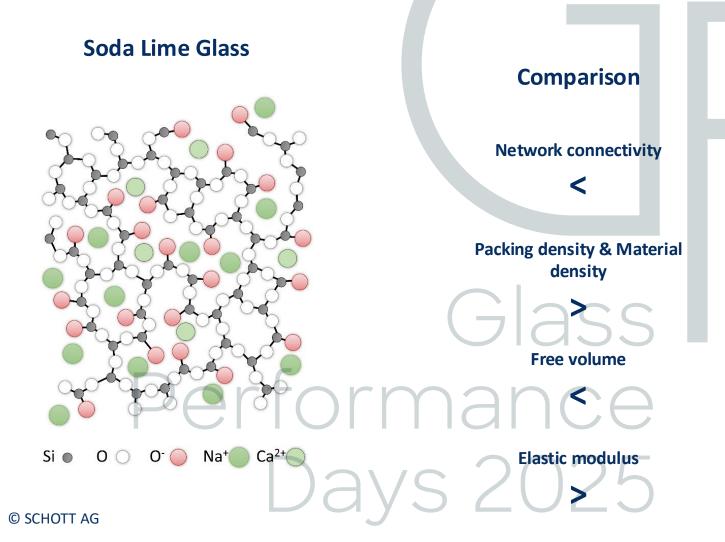

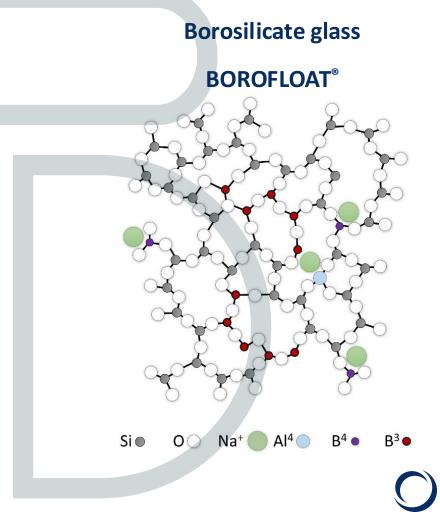

Vickers Sharp Impact Test on Laminates

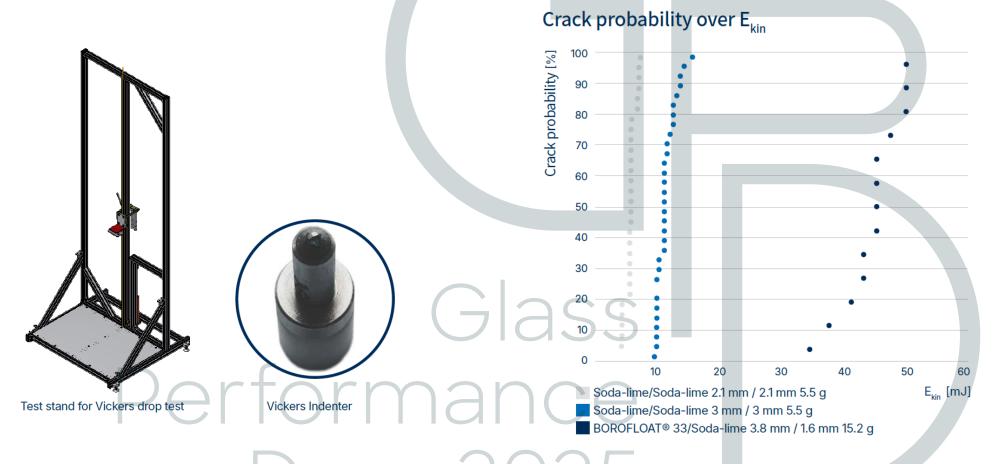




This technical information is limited to the information about the test results in SCHOTT's laboratories. Processors have to evaluate the mechanical resistance in the relevant end product. Different designs and processing methods (e.g. coating, different laminate setups, thermal treatment, and others) might influence the properties and results of the mechanical resistance in the relevant end product.



Vickers Sharp Impact Test on Laminates

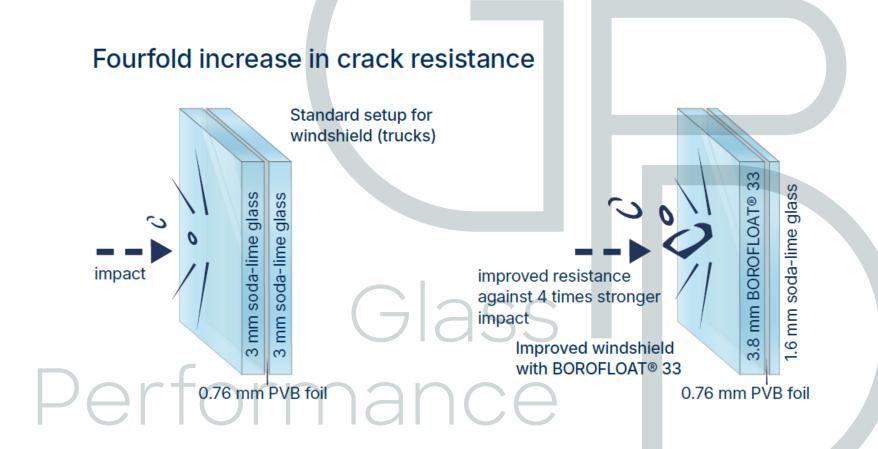



This technical information is limited to the information about the test results in SCHOTT's laboratories. Processors have to evaluate the mechanical resistance in the relevant end product. Different designs and processing methods (e.g. coating, different laminate setups, thermal treatment, and others) might influence the properties and results of the mechanical resistance in the relevant end product.



Borosilicate glass is a good material for the outer pane of the windshield

Performance Days 2025 Good windshield bending furnace is needed for bending of borosilicate glass and soda-lime glass combination

Typical windscreen bending furnace



First tests with small glass sizes



Bending tests for borosilicate – soda-lime glass combination

Glass size 500 mm x 300 mm

Top glass:

Soda-lime

-Thickness 1.6 – 5.8 mm


Bottom glass:

Borofloat® 33

- Thickness: 2.0 - 3.8 mm



Viscosity and thermal expansion coefficient are different between borosilicate and soda-lime glasses

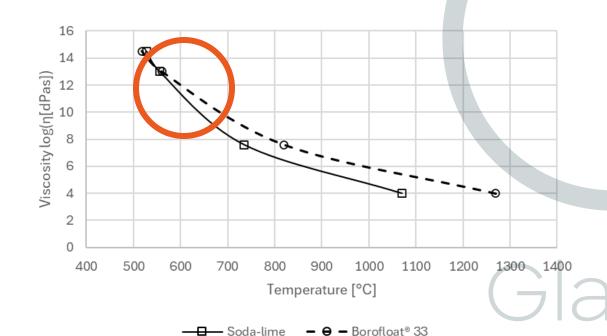

Thermal expansion coefficients

@ 0-300 °C

Sodalime glass

• 9·10⁻⁶ 1/K

Borofloat® 33

◆ 3.25·10⁻⁶ 1/K

Performance Days 2025



Hotspots on soda-lime glass



Effect of glass thickness combination and bending temperature on bending quality

	Glass thickness [mm]		Final furnace	Final Visual quality		uality
	Borofloat®	soda-lime	bottom temp	furnace top	Borofloat®	soda-lime
Test #	33	soua-iiiie	[°C]	temp [°C]	33	Soua-IIIIe
1	3.3	2.1	701	609	Ok	hotspots
2	2	2.1	685	595	Ok	Ok
3	2	1.58	687	576	Ok	hotspots
4	3.3	3.1	707	615	Ok	hotspots
5	3.8	6	714	605	Ok	hotspots
6	3.8	1.58	638	612	Ok	hotspots
7	3.8	1.58	634	609	Ok	hotspots
8	2.75	1.58	648	600	Ok	hotspots
9	2.75	2.6	648	680	Ok	hotspots
10	2.75	2.6	623	596	Ok	Ok
11	2.75	3.1	625	599	Ok	Ok
12	3.3	1.58	630	604	Ok	Ok
13	3.3	1.58	629	603	Ok	Ok
14	3.3	1.58	651	606	Ok	Ok



Windshield bending with full size borosilicate (3.8 mm) – soda-lime (1.6 mm) combination




Bending process causes optical changes in windshield





Bending process causes optical changes in windshield





Challenges when changing outer glass from soda-lime glass to borosilicate glass

Higher bending temperature

More heating needed from bottom side (borosilicate glass)

Davs 2025

Soda-lime glass will easily overheat

• Optical quality issues



With flexible windshield bending furnace the bending of borosilicate and soda-lime glass combination is possible